

NOVELTIES FROM ABROAD.

Worsted Dressgood. (Double Face Effect.)

Warp: 8000 ends.

Weave: See Diagram Fig. 1; repeat 16 warp threads and 8 picks; 16-harness straight draw.

Reed: $17\frac{1}{2}$ @ 8 ends per dent; 140 ends per inch; $57\frac{1}{4}$ inches wide in reed.

Dress: 1 end 2/70's worsted, navy blue } 43 times
1 " 2/64's " , red }
1 " 2/70's " , white (bleached)
1 " 2/64's " , red

88 ends in repeat of pattern.

Filling: 60 picks per inch, all single 36's worsted, navy blue.

Finish: Worsted finish; 52 inches wide.




Fig. 1



Fig. 2



Fig. 3

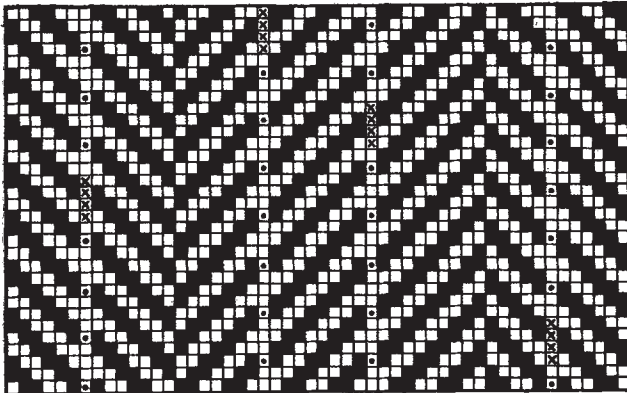


Fig. 4

Worsted Cheviot Dressgood.

(Herringbone Face with Stripe Effect Back.)

Warp: 2912 ends.

Weave: See Diagram Fig. 3; repeat 48 warp threads and 8 picks; 8 or 12-harness fancy draw.

Reed: 21 { 2 dents @ 4 ends } 63 $\frac{1}{2}$ " wide in reed.
20 " " 2 " }

($2912 \div 48 = 60\frac{2}{3} \times 22 = 1334 \div 21 = 63\frac{1}{2}$)

Dress: 2 ends 2/48's worsted, bronze
1 end 2/40's " , gray green mix } 3 times
1 " 2/48's " , bronze }
40 ends 2/40's " , gray green mix
2 " 2/48's " , deep sky blue
1 end 2/40's " , gray green mix } 3 times
1 " 2/48's " , deep sky blue }
40 ends 2/40's " , gray green mix

96 ends in repeat of pattern.

Filling: 44 picks per inch, all 2/40's worsted, light gray mix.

Finish: Worsted cheviot finish; full 12 per cent in length and to 56 inches wide.

Piece Dyed Worsted Dressgood. (Stripe Effect.)

Warp: 5712 ends.

Weave: See Diagram Fig. 2; repeat 32 warp threads and 4 picks; 4, 6, 8, 10 or 12-harness fancy draw.

Reed: 21 @ 4 ends per dent; 84 ends per inch; 68 inches wide in reed.

Dress: 4 ends 2/70's worsted, white
1 end 2/60's merc. cotton, peacock blue
14 ends 2/70's worsted, white
2 " 2/64's worsted, black
30 " 2/70's worsted, white
2 " 2/64's worsted, black
11 " 2/70's worsted, white

64 ends in repeat of pattern.

Filling: 75 picks per inch, all 2/70's worsted, white.

Finish: Scour well, dye navy blue, scour, shear, thread bare, press; 60 inches wide. Besides the Herringbone effect, two fine stripe effects (black and peacock blue) will show.

Worsted Cheviot Dressgood. (Spot Effect.)

Warp: 2912 ends; 2688 ends ground (see full type) and 224 ends figure (see cross and dot type).

Weave: See Diagram Fig. 4; repeat 52 warp threads and 32 picks; 8, 12 or 16-harness fancy draw.

Reed: $10\frac{1}{2}$ { 1 dent @ 4 ends }
1 " " 5 " } 64" wide in reed.
1 " " 4 " }

Dress: 1 end 2/36's worsted, bleached-white } 3 times
1 " " " , green-white }
1 " 2/36's worsted, lilac
1 " 2/36's worsted, bleached-white } 7 times
1 " " " , green-white }
1 " 2/36's worsted, green
1 " 2/36's worsted, bleached-white } 4 times
1 " " " , green-white }
1 " 2/36's worsted, yellow
1 " 2/36's worsted, bleached-white } 7 times
1 " " " , green-white }
1 " 2/36's worsted, green
1 " 2/36's worsted, bleached-white } 3 times
1 " " " , green-white }

52 ends in repeat of pattern.

Filling: 2 picks 2/36's worsted, bleached-white
2 " " " , olive-white

4 picks, repeat of pattern.

Finish: Cheviot finish; 52 inches wide.

HARRIS TWEED.

The Hebridean Islanders have now been successful in obtaining the protection of *Harris tweed* by a registered trade mark, under new Board of Trade regulations. The Hebridean cloth is now legally defined as "a tweed hand-spun, hand-woven, dyed and finished by hand in the Islands of Lewis, Harris, Uist, Barra, and their several purlenances, and all known as the Outer Hebrides." Any one in future selling as *Harris tweed* material which does not answer to this description will be liable to prosecution.